

Detailed Study on the Strength Properties of Sustainable Concrete

KP.Muhammed Nisham ¹, K.C Denesh. ²M.Yeswanth ³, KU.Manikandhan ⁴

¹PG Student Nandha Engineering College ,Erode.

^{2,3,4}Assistant Professor, Nandha Engineering College ,Erode.

Abstract : Conventional concrete is responsible for amount of carbon-dioxide emission to some extent. So to reduce the emission, various types of concrete are developed using waste products from industries and agricultural use like blast furnace slag, silica fume, fly ash which requires low amount of energy and also cause least harm to the environment. Green concrete is a new technology developed now days to reduce the effect on environment by production of cement. Cement contains high amount of carbon-di-oxide which harms the environment drastically, so by replacing the cement by various materials which causes harm to the environment we not only reduce the problem of disposal of these materials but we reduce the emission of carbon-di- oxide from cement and as a result of which we reduces the negative effect on environment.

Keywords - Green Concrete, Silica fume, Demolished Brick Aggregate, CO₂ Emission, Eco-Friendly concrete.

I. INTRODUCTION

Color has nothing to do with green concrete. It is a concept of thinking and environment into an every aspect of the raw materials manufacture over construction, mixture design to structural design, and durability. Green concrete is very often considered to be cheap to produce due to the use of recycled material whereby avoiding the charges for the disposal of waste, less energy consumption and greater durability.

While a normal construction practices are guided by short term economic considerations, sustainable construction is focused on best practices which emphasize on long term affordability, durability and effectiveness. At each stage of the life cycle of the construction, it increases ease and quality of life, while minimizing the negative environmental impacts and increasing economic sustainability of the construction. Any infrastructure designed and constructed in a sustainable way minimizes the use of resources through the whole life cycle of the construction process in which the green concrete play a vital role in achieving the sustainable construction. Having so much of advantageous has led to popularity in construction world and one of the emerging technology in sustainable construction. Green concrete is miracle of present and tool for future when the natural resources are on the verge of extinction. Due to growing interest in sustainable development, engineers and architects are motivated more than ever before to choose materials that are more sustainable. Selection of material for concrete is more sustainable and minimizes environmental impact. Cement production accounts for more than 6% of all CO₂ emission which is a major factor in the world's global warming (Greenhouse gas). India is the third largest cement producer in the World and one of the largest consumers of cement per capita in the world. Rough figures are that India consumes about 1.2 Ton/year/capita, while as World average is 0.6 Ton/year/capita. CO₂ emissions from 1 ton of concrete produced vary between 0.05 to 0.13 tons. 95% of all CO₂ emissions from a cubic meter of concrete are from cement manufacturing.

Cement is the one of the major component of the concrete. The production of one ton of cement releases one ton of a CO₂ into the atmosphere. CO₂ is known to be greenhouse gas that contributes to the global warming. The reduction in CO₂ emission from a concrete can be achieved with a partial replacement of cement by the various supplementary cementitious materials. The use of these cementitious materials has resulted in an improvement of the properties of concrete.

So to reduce this environmental impact green concrete plays a vital role. By using recycled materials or waste materials which are harmful to the environment as a replacement of cement such as fly ash, silica flume, etc. we can reduce the CO₂ emission from concrete as well as it reduces the environmental impact on earth. As a result of which green concrete is one of the major tool in the future when the natural resources are on verge of extinction.

II.OBJECTIVES

- 1) To study the effect of silica fume on the environment.
- 2) To study the effectiveness of concrete by partial replacement of cement by silica fume and Course aggregate by demolished brick.

- 3) To determine the strength of new mix design concrete of grade M40.
- 4) To determine the various test results like compression test, flexural test & split tensile test.
- 5) To find the optimum percentage of silica fume in cement so that we can achieve maximum strength by increasing percentage as 5%,10%,15%,20%.

2. METHODOLOGY

- To find out number of literature on green concrete.
- To study about the ingredients of green concrete.
- Collection of various ingredients required for project from different outsources.
- To design a concrete mix for M40 grade as per the Indian Standard Recommended method.
- To cast cubes, beams & cylinders by using a various ingredients as per mix design.
- To test the casted cubes, beams & cylinders for strength after 7, 14, 28 days of curing respectively by performing various test like compressive test, flexural test & split tensile test.
- To calculate the economy for green concrete.
- To compare between conventional concrete and green concrete based on various parameters.

4) EXPERIMENTAL WORK

4.1 CEMENT

Ordinary Portland cement grade 53, manufactured by Birla .super confirming to IS 12269 – 2013.

Table No. 1: Properties of Cement

Sr. No.	TESTS	STANDARD VALUES	OBTAINED VALUES
1.	Normal Consistency	-	29%
2.	Initial Setting Time	>30 Min	42 Min
3.	Specific Gravity	3.10-3.20	3.15
4.	Fineness	<10%	0.8%

4.2 FINE AGGREGATE

Artificial sand passing through 4.75 mm IS sieve & retained on 150 micron confirming to IS 383 – 1970.

Table No. 2: Properties of Fine Aggregate

3.	Grading Zone	I-IV	II
----	--------------	------	----

4.3 COARSE AGGRGATE

Sr. No.	TESTS	STANDARD VALUES	BTAINED VALUES
1.	Specific Gravity	2.50-3.00	2.90
2.	Water Absorption	0.5%-1.0%	1%
3.	Grading Zone	I-IV	II

20mm size coarse aggregates confirming to IS 383 – 1970. Table No. 3: Properties of Course Aggregate

4.4 DEMOLISHED BRICKS

Demolished bricks were collected from the demolished building of age 50 years. The collected sample were

broken manually into pieces of size passing through 4.75mm IS sieve and retained on 150 micron IS sieve.

Table No. 4: Properties of Demolished Brick Wastes

Sr. No.	TESTS	STANDARD VALUES	OBTAINED VALUES
1.	Specific Gravity	1.80-2.0	1.96
2.	Water Absorption	28%-30%	30%

4.5 MICRO SILICA

Silica fume used was conforming to ASTM – C (1240 – 2000) and was supply by “ELKEM INDUSTRIES” was name Elkem – Micro Silica 920 D. The silica fume is used as a partial replacement of cement.

Table No. 5: Properties of Micro Silica

Sr. No.	PROPERTIES	STANDARD VALUES
1	Specific Gravity	2.2
2	Bulk Density	576 (Kg/m3)
3	Size (Micron)	0.1-0.2

Sr. No.	TESTS	STANDARD VALUES	OBTAINED VALUES
1.	Specific Gravity	2.50-2.80	2.53
2.	Water Absorption	1%-2%	1.2%


5.1 MIX DESIGN

Mix design was done based on IS 10262 – 1982 & IS 456 – 2000 for M40 grade of concrete.

Following shows the mix proportion of concrete per m³

- Cement Content : 430.00 Kg
- Fine Aggregate : 717.50 Kg
- Coarse Aggregate : 1233.66 Kg
- Admixtures (BSF) : 5.16 Kg
- W/C Ratio : 0.35
- Cement : Fine Aggregate : Coarse Aggregate 1 : 1.66 : 2.93

5.2 EXPERIMENTAL PROCEDURE

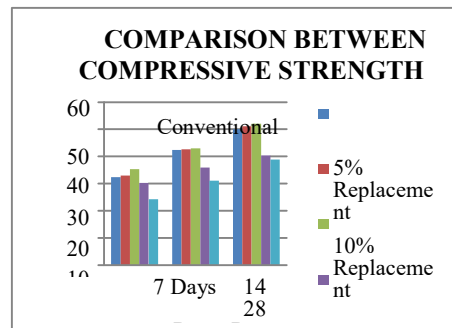

The specimen of standard cube of 150mm*150mm*150mm and standard cylinder of 300mm*150mm and prism of size 100mm*100mm*500mm were used to determine the compressive strength, split tensile strength and flexural strength of concrete.

6. TEST RESULTS & DISCUSSION

6.1 Compression Test

The test was carried out confirming to IS 516 – 1959 to obtain compressive strength of concrete at the age of 7, 14, 28 days. The cubes were tested using Compression Testing Machine (CTM) of capacity 2000 KN.

Table no. 5: Results of compression test

6.2 Flexural Test

The test was carried out confirming to IS 516 – 1959 to obtain flexural strength of concrete at the age of 14 & 28 days. The cubes were tested using Universal Testing Machine (UTM) of capacity 600 KN.

% SILICA	% BRICK AGGREGATE	FLEXURAL STRENGTH (MPa)	
		14 DAYS	28 DAYS
0%	0%	4.68	5.96
5%	50%	4.93	6.21
10%	50%	4.98	6.40
15%	50%	4.59	5.70
20%	50%	4.37	5.56

Table no.6: Results of flexural test

Split Tensile Test

The test was carried out confirming to IS 516 – 1959 to obtain flexural strength of concrete at the age of 14 & 28 days. The cubes were tested using Universal Testing Machine (UTM) of capacity 600 KN.

Table no.7: Results of split tensile test

% SILICA	% BRICK AGGREGATE	SPLIT TENSILE STRENGTH (MPa)	
		14 DAYS	28 DAYS
0%	0%	1.63	2.78
5%	50%	2.00	3.51
10%	50%	2.38	3.90
15%	50%	1.60	2.71
20%	50%	1.40	2.25

9. CONCLUSION

Silica fume is a material which may cause air pollution; this is the byproduct of some industries. Addition of micro silica in cement reduces the air pollution and makes concrete more sustainable; as well as the optimum replacement of cement with silica 5% to 15% leads to increase in strength whereas the 20% replacement leads to decrease in strength of concrete. Silica fume is finer than cement and more reactive to concrete ingredients so it increases the normal consistency of cement and achieves more strength in less time as compare to conventional

concrete. By replacing the fine aggregate with demolished brick waste, there is no significant effect on any strength of concrete, but the overall cost of concrete reduces up to 20% so economically the concrete is more economical than conventional concrete

REFERENCES

- [1] Anita Bhatia, Rashmy Nair & Neeru Gakkhar, 2016 "Green Concrete A Stepping Stone For Future," International Journal of Engineering Research & Management Technology 3(1).
- [2] Praveer Singh, Mohd. Afaque Khan & Abhishek Kumar 2016 "The Effect on Concrete by Partial Replacement of Cement by Silica Fume," International Research Journal of Engineering and Technology 3(3).
- [3] Tae Hyoung Kim, Chang U Chae, Gil Hwan Kim & Hyoung Jae Jang 2016 "Analysis of CO2 Emission Characteristics of Concrete Used at Construction Sites,"
- [4] Kasi Rekha, Dr. M. Potharaju 2015 "Residual Compressive Strength of Recycled Brick Aggregate Concrete at High Temperatures," International Journal of Emerging Technology and Advanced Engineering 5(1)
- [5] Dhiraj Kumar Tiwari, Ankur Rai, Jagrit Dewan & Rohit Mathew, 2015 "Comparative Study on Green Concrete," International Journal Of Advanced Research In Engineering Technology & Sciences 2(4).
- [6] Xian LI, Fujin WANG, Fei LI 2015 "Effect of Recycled Waste Brick Fine Aggregate on Compressive Strength and Flexural Strength of Mortar," 5th International Conference on Civil Engineering and Transportation.
- [7] Kakamare M.S. & Nair V.V., 2015 "Sustainable Construction Materials And Technology: Green Concrete," International Journal of Advanced Technology in Engineering and Science 3(2).
- [8] Mohammed Tarek Uddin1, Ali Zafar Khan, Aziz Hasan Mahmood. 2015 "Recycling of Demolished Brick Aggregate Concrete as Coarse and Fine Aggregates."
- [9] Dewanshu Ahlawat, L.G.Kalurkar 2014 "Coconut Shell as Partial Replacement of Coarse Aggregate in Concrete," International Conference on Advances in Engineering & Technology.
- [10] Abhijeet Baikerkar, 2014 "A review on green concrete," Journal of Emerging Technologies and Innovative Research 1(6).
- [11] Chirag Garg & Aakash Jain, 2014 "Green Concrete: Efficient & Eco-friendly Construction Materials," International Journal of Research in Engineering & Technology 2(2).
- [12] C.Nagarajan and M.Madheswaran - 'Experimental verification and stability state space analysis of CLL-T Series Parallel Resonant Converter' - Journal of ELECTRICAL ENGINEERING, Vol.63 (6), pp.365-372, Dec.2012.
- [13] C.Nagarajan and M.Madheswaran - 'Performance Analysis of LCL-T Resonant Converter with Fuzzy/PID Using State Space Analysis' - Springer, Electrical Engineering, Vol.93 (3), pp.167-178, September 2011.
- [14] C.Nagarajan and M.Madheswaran - 'Stability Analysis of Series Parallel Resonant Converter with Fuzzy Logic Controller Using State Space Techniques' - Taylor & Francis, Electric Power Components and Systems, Vol.39 (8), pp.780-793, May 2011.
- [15] C.Nagarajan and M.Madheswaran - 'Experimental Study and steady state stability analysis of CLL-T Series Parallel Resonant Converter with Fuzzy controller using State Space Analysis' - Iranian Journal of Electrical & Electronic Engineering, Vol.8 (3), pp.259-267, September 2012.
- [16] Nagarajan C., Neelakrishnan G., Akila P., Fathima U., Sneha S. "Performance Analysis and Implementation of 89C51 Controller Based Solar Tracking System with Boost Converter" Journal of VLSI Design Tools & Technology. 2022; 12(2): 34-41p.
- [17] C. Nagarajan, G.Neelakrishnan, R. Janani, S.Maithili, G. Ramya "Investigation on Fault Analysis for Power Transformers Using Adaptive Differential Relay" Asian Journal of Electrical Science, Vol.11 No.1, pp: 1-8, 2022.
- [18] G.Neelakrishnan, K.Anandhakumar, A.Prathap, S.Prakash "Performance Estimation of cascaded h-bridge MLI for HEV using SVPWM" Suraj Punj Journal for Multidisciplinary Research, 2021, Volume 11, Issue 4, pp:750-756
- [19] G.Neelakrishnan, S.N.Pruthika, P.T.Shalini, S.Soniya, "Perfromance Investigation of T-Source Inverter fed with Solar Cell" Suraj Punj Journal for Multidisciplinary Research, 2021, Volume 11, Issue 4, pp:744-749
- [20] C.Nagarajan and M.Madheswaran, "Analysis and Simulation of LCL Series Resonant Full Bridge Converter Using PWM Technique with Load Independent Operation" has been presented in ICTES'08, a IEEE / IET International Conference organized by M.G.R.University, Chennai.Vol.no.1, pp.190-195, Dec.2007
- [21] M Suganthi, N Ramesh, "Treatment of water using natural zeolite as membrane filter", Journal of Environmental Protection and Ecology, Volume 23, Issue 2, pp: 520-530,2022
- [22] M Suganthi, N Ramesh, CT Sivakumar, K Vidhya, "Physiochemical Analysis of Ground Water used for Domestic needs in the Area of Perundurai in Erode District", International Research Journal of Multidisciplinary Technovation, pp: 630-635, 2019
- [23] Umesh Sharma, Ankita Khatri & Abhishek Kanoungoc 2014 "Use of Micro-silica as Additive to Concrete-state of Art," International Journal of Civil Engineering Research 5(1).
- [24] N. K. Amudhavalli & Jeena Mathew, 2012 "Effect Of Silica Fume On A Strength & Durability Parameters Of Concrete," International Journal of Engineering Sciences & Emerging Technologies 3(1).
- [25] Verma Ajay, Chandak Rajeev & Yadav R.K. 2012 "Effect of Micro Silica on The Strength of Concrete with Ordinary Portland Cement," Research Journal of Engineering Sciences 1(3).